

Dragonshine Industrial (HK) Limited

TEST REPORT

SCOPE OF WORK

Woven vinyl flooring

REPORT NUMBER

220309010SHF-001

TEST DATE(S)

2022-03-09 - 2022-03-29

ISSUE DATE

2022-03-29

PAGES


6

DOCUMENT CONTROL NUMBER

LFT-APAC-SHF-OP-10k(May 1, 2021)

© 2021 INTERTEK

Intertek Testing Services Shenzhen Ltd. Shanghai Fengxian Branch

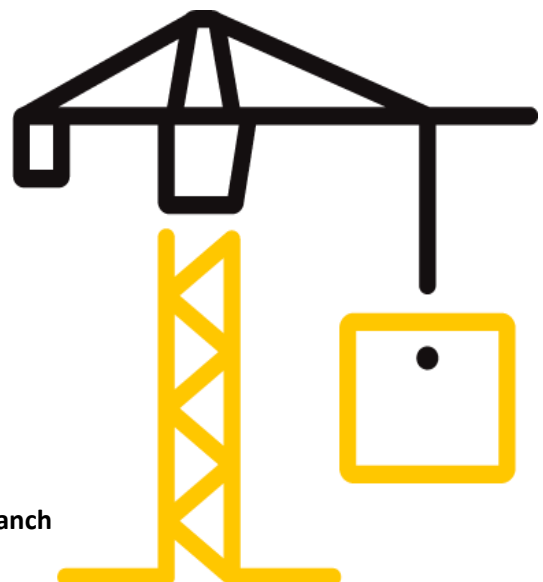

Test Report

Statement

- 1.This report is invalid without company's special seal for testing on assigned page.
- 2.This report is invalid without authorized person's signature.
- 3.This report is invalid where any unauthorized modification indicated.
- 4.Don't copy this report in partial (except full copy) without any official approval in written by our company. This report is invalid without re-stamping the special seal for testing in copying report.
- 5.Any holder of this document is advised that this report is for the exclusive use of Intertek's Customer and is provided pursuant to the agreement between Intertek and its Customer. Intertek's responsibility and liability are limited to the terms and conditions of the agreement. This report was made with due care within the limitation of a defined scope of work and on the basis of information, materials and instructions received from the Customer or its nominated third parties. Intertek is under no obligation to refer to or report upon any facts or circumstances which are outside the specific instructions received and accepts no responsibility to any parties whatsoever, following the issue of the report, for any matters arising outside the agreed scope of the works. The tests results are not intended to be a recommendation for any particular course of action. Customer is responsible for acting as it sees fit on the basis of such results.
- 6.Intertek's written consent is required to use Intertek's name or logo on the object, product or service being tested. The observations and test results in this report relate only to the sample under test. This report alone does not indicate that the item, product or service has passed any Intertek certification program.
- 7.The report was digital signed by Shang Hai, Intertek Group plc, please using Adobe Acrobat Reader to verify the authenticity.



Test Report

Issue Date: 2022-03-29 Intertek Report No. 220309010SHF-001

Applicant: Dragonshine Industrial (HK) Limited

Address: A302, Meidu Plaza, no.789, Moganshan RD, 310011

Attn: Shell

Test Type: Performance test, samples provided by the applicant.

Product Information

Product Name	Woven vinyl flooring	Brand	texlyweave
Sample Description	Good Condition	Sample Amount	9 pcs
		Received Date	2022-03-08
Sample ID	Model	Specification	
S220309010SHF.001~002	13019	50*50cm	

Test Methods And Standards

Test Standard	ISO 8301:1991/Amd1:2010, With reference to EN 986:2005
Specification Standard	/
Test Conclusion	The samples were tested according to the above standards, and the results are shown in the following page.


Note:

1.This report relates specifically to the sample(s) that were drawn and provided by the applicant or their nominated third party. The reported result(s) provide no warranty or verification on the sample(s) representing any specific goods and/or shipment and only relate to the sample(s) as received and tested.

Report Authorized







Name: Daniel Zhang Name: Sally Xie Name: Erin Huang
Title: Approver Title: Reviewer Title: Project Engineer

Test Report

Issue Date: 2022-03-29

Intertek Report No. 220309010SHF-001

Test Items, Method and Results:

Test Item: Thermal conductivity and thermal resistance

Test Method: ISO 8301:1991/Amd1:2010

Conditioning: Condition the test specimen at (23±2)°C and (50±5)% relative humidity to constant mass

Test Result:

Sample	Thickness	Mean Temperature	Temperature Difference	Thermal Conductivity	Thermal Resistance
	(mm)	(°C)	(°C)	(W/m·K)	(m ² ·K)/W
1	3.30	24.4	13.9	0.077	0.043
2	3.35	24.3	13.9	0.076	0.044
3	3.29	24.2	14.1	0.064	0.051
Average	3.31	24	14	0.072	0.046

Test Report

Issue Date: 2022-03-29

Intertek Report No. 220309010SHF-001

Test Items, Method and Results:

Test Item: Dimensional stability

Test Method: With reference to EN 986:2005

Test Condition: Stage 1: Place the test specimen in the oven at (60±2)°C for 2h

Stage 2: Immerse the test specimen flat in the water at (20±2)°C for 2h

Stage 3: Place the test specimen in the oven at (60±2)°C for 24h

Stage 4: Re-condition the specimen in the standard atmosphere for 48h

Test Result:

Test Item	Test Result			
Dimensional stability	Change after Stage 1:	Direction 1:	0.01	%
		Direction 2:	-0.03	%
	Change after Stage 2:	Direction 1:	-0.02	%
		Direction 2:	-0.04	%
	Change after Stage 3:	Direction 1:	-0.03	%
		Direction 2:	-0.06	%
	Change after Stage 4:	Direction 1:	-0.02	%
		Direction 2:	-0.03	%




Test Report

Issue Date: 2022-03-29

Intertek Report No. 220309010SHF-001

Appendix A: Sample Received Photo

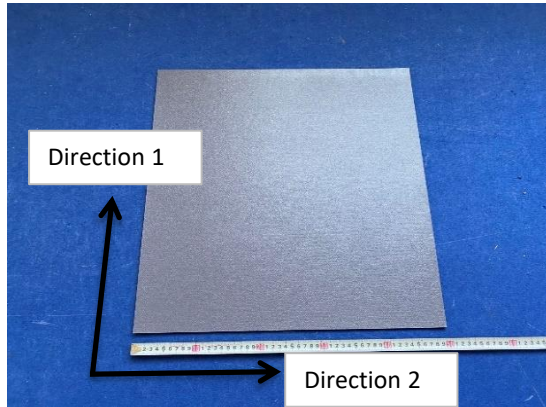

Revision:

NO.	Date	Changes
220309010SHF-001	2022-03-29	First issue